

RULES FOR APPROVAL OF MANUFACTURERS AND SERVICE SUPPLIERS

Rules for Approval of Manufacturers and Service Suppliers
2009 AMENDMENT NO.1

Rule No.18 15th April 2009

Resolved by Technical Committee on 4th February 2009

Approved by Board of Directors on 24th February 2009

ClassNK
NIPPON KAIJI KYOKAI

AMENDMENT TO THE RULES FOR APPROVAL OF MANUFACTURERS AND SERVICE SUPPLIERS

“Rules for approval of manufacturers and service suppliers” has been partly amended as follows:

Amendment 1-1

Part 3 REQUIREMENTS FOR APPROVAL OF SERVICE SUPPLIERS

Chapter 5 Firms Engaged in Performance Tests of VDRs

Section 5.2 has been amended as follows.

5.2 ~~Operators and Supervisors~~ Firms

5.2.1 Education and Training

~~1 Operators carrying out performance tests of VDRs and supervisors are to have sufficient knowledge upon the following (1) through (3):~~

Firms responsible for the carrying out of performance tests on VDRs are to maintain those up-to-date versions of the books and documents referred to in the following (1) through (3):

- (1) The requirements of VDRs and the inspection instructions issued by the Society
- (2) The latest *SOLAS (Safety of life at sea)*, *IMO (International Maritime Organization)* Assembly Resolution concerning performance standards, and *IEC (International Electrotechnical Commission)* standards
- (3) The following reference documents concerning VDRs in question
 - (a) Installation manual
 - (b) Operation and maintenance manual
 - (c) Information for use by an investigation authorities

~~2 The documented training procedures specified in 1.2.2 are to contain the followings.~~

- (1) Procedures to learn the knowledge specified in -1 above
- (2) Procedures for the continuous ~~internal~~ education and training of the suppliers

5.2.2 Qualifications, etc

~~1 In general, one or more operators and supervisors are to be attached to the suppliers respectively.~~

~~21 As for the competence and experience, operators for the performance tests of VDRs are to comply with the requirements specified in (1) and (2).~~

Firms responsible for the carrying out of performance tests on VDRs are to comply with the requirements specified in the following (1) and (2):

- ~~(1) Operators carrying out the performance tests of VDRs are to have qualifications approved by the manufacturer.~~
- ~~(2) Operators are to have experience as an operator of VDRs for one year or more as well as to have once or more experience for performance tests.~~
- (1) Firms are to provide evidence that they have been authorized or licensed by the relevant manufacturer to carry out performance tests on VDRs.

(2) In general, one or more qualified operators and supervisors (as specified below) are to be assigned to suppliers respectively.

- i) Operators : Those persons who have qualifications approved by the relevant manufacturer for the carrying out of performance tests on VDRs and have one year or more prior experience as a sub-operator of VDRs as well as have conducted such performance tests at least once before.
- ii) Supervisors : Those persons who have 2 or more years experience as an operator of VDRs.

2 Notwithstanding -1 above, the Society may appoint a firm as the firm responsible for carrying out the performance tests of VDRs that is deemed to have qualifications equivalent to those specified in -1.

~~3 As for the competence and experience, supervisors for performance tests of VDRs are to comply with the requirements specified in (1) and (2).~~

~~(1) Supervisors carrying out the performance tests of VDRs are to have qualifications approved by the manufacturer.~~

~~(2) Supervisors are to have experience as a supervisor of VDRs for 2 years or more.~~

~~4 Notwithstanding -1 through -3 above, the Society may appoint a person as an operator or a supervisor of VDRs who is deemed to have competence and experience equivalent to those specified in -1 through -3.~~

5.3 Equipment for the Performance Tests of VDRs

Paragraph 5.3.1 has been amended as follows.

5.3.1 Equipment for the performance tests of VDRs

~~The suppliers Firms~~ are to have the equipment specified in the following (1) through (3) available for the carrying out of performance tests of on VDRs; specified in the following (1) through (3).

- (1) Instruments for measuring frequency, voltage, current and resistance
- (2) Playback hardware of recorded data, speakers, printers and memories
- (3) Playback software of recorded data

EFFECTIVE DATE AND APPLICATION (Amendment 1-1)

- 1.** The effective date of the amendments 15 April 2009.

Part 3 REQUIREMENTS FOR APPROVAL OF SERVICE SUPPLIERS

Chapter 9 FIRMS ENGAGED IN TESTING OF COATING SYSTEMS

9.2 Initial Assessment

9.2.1 Initial Assessment

Sub-paragraph 9.2.1-1 has been amended as follows.

1 Initial Assessment

Firms engaged in testing of coating systems is to submit 3 copies each of the following documents in addition to the documents specified in **2.3-1, Part 1. Report forms for the test procedures for coating qualification and crossover tests are to be as referred to Form 9-1 and 9-2.**

- (1) A detailed list of the Laboratory test equipment for the IMO Resolution MSC.215(82) as may be amended coating approval
- (2) A detailed list of reference documents comprising a minimum those referred to in MSC.215(82) as may be amended that are available in the laboratory
- (3) Details of testing panel preparation, procedure of test panel identification, coating application, test procedures and a sample test report
- (4) Details of exposure method and site for weathering primed test panels
- (5) A sample daily or weekly log/form for recording test condition and observations including unforeseen interruption of the exposure cycle with corrective actions
- (6) Details of any sub-contracting agreements
- (7) Comparison test report with an approved coating system or laboratory if available

Form 9-1 and 9-2 have been added as follows.

Form 9-1

EXAMPLE COATING PRODUCER

**BALLAST TANK COATING TEST OF 2 * 160 μ M EXAMPLE EPOXY PAINT
ON EXAMPLE SHOP PRIMER**

Table of contents

1	Summary
2	Scope of work
3	Work carried out prior to exposure
3.1	Identification
3.2	Surface preparation
3.3	Application
3.3.1	Application procedure
3.3.2	Coding
3.4	Dry film thickness
3.5	Pin hole detection
4	Exposure
5	Tests carried out after exposure
6	Test results
7	Conclusion
8	References
9	Appendix A - Environmental data - weathering of shop primed panels
10	Appendix B - Details of surface preparation, application and test results
11	Appendix C - Photo documentation
12	Appendix D - Infrared Scanning Charts

1 SUMMARY

The coating system, 2 * 160 µm Example Epoxy Paint from Example Coating Producer, applied to Example zinc silicate shop primed panels has been tested in accordance with the IMO Performance Standard for protective Coatings /1/. The coating was applied after 2 months weathering of the shop primer.

The results from the testing show that the Example Epoxy Paint from Example Coating Producer has passed all the requirements given in the Performance Standard for Protective Coatings /1/.

2 SCOPE OF WORK

The following work and tests have been performed:

- Identification of the coating system
- Film thickness measurements and pin hole detection on panels before testing
- 180 days testing in condensation chamber
- 180 days testing in wave tank
- 180 days testing in heating cabinet
- Evaluation of results after testing, including blister detection, undercutting from scribe, adhesion and coating flexibility
- Evaluation of cathodic protection during testing (wave tank)

3 Work carried out prior to exposure

3.1 Identification

The coating system was identified by infrared scanning (by means of a(name and model of the instrument)) and by determination of specific gravity (according to ISO 2811 -1) by means of an Pyknometer (name and model of the instrument) .

3.2 Surface preparation

Surface preparation was carried out according to the data given in Table B-1 Appendix B.

3.3 Application

3.3.1 Application procedure

Example zinc silicate shop primer was applied to the blast cleaned panels according to the data given in Table 2. The shop primed panels were then exposed out-door for 2 months. The environmental data for the exposure period is given in Appendix A.

Two coats (specified dry film thickness 160 µm per coat) of Example Epoxy Paint were applied to the weathered and cleaned zinc silicate shop primed panels. The application data are given in Table B-2 Appendix B.

3.3.2 Coding

The panels were coded as shown in Figure B-1 in Appendix B.

3.4 Dry film thickness

The dry film thickness measurements were carried out by means of a (name and model of the instrument) dry film thickness unit before testing. Templates, as given in Figure B-2 in Appendix B, were used for the measurements. The results from the measurements are given in Table B-3 in Appendix B.

3.5 Pin hole detection

Pin hole detection was performed on the coated test panels before testing. The detection was carried out by means of a (name and model of the instrument) Pinhole detector at 90 volts.

4 EXPOSURE

The testing was carried out according to the IMO Performance Standard for Protective Coatings /1/. The exposure was started 02.11.07 and terminated 14.06.08.

5 TESTS CARRIED OUT AFTER EXPOSURE

Evaluation of blisters and rust, adhesion, undercutting from scribe and flexibility was carried out according to specifications and standards referred to in the IMO Performance Standard /1/.

6 TEST RESULTS

The results of the product identification are given in Table 1.

The results of the examination of the coated test panels are schematically given in Table 2 and more detailed in Appendix B. Pictures of the panels after exposure are enclosed as Appendix C.

Table 1 Results of analyses (Product identification)

Product	Batch no.	IR identification (main components)	Specific gravity (g/cm ³)
Example, part A	123	Ethyl silicate	0.93
Example, part B	234	NA*	2.21
Example Epoxy Paint Grey, base	345	Epoxy	1.48
Example Epoxy Paint hardener	456	Amide	0.96
Example Epoxy Paint Buff, base	567	Epoxy	1.47

* Identified and spectres stored. No generic correlation to the spectres in the data base found.

Table 2 Results of examination of the coated test samples

Test parameter	Acceptance criteria	Test results	Passed / failed
Pin holes (no)	No pinholes	0	Passed
Blisters and rust (all panels) ¹⁾	No blisters or rust	0	Passed
Adhesion values (MPa) – wave tank panels ²⁾	>3.5 adhesive failure >3.0 cohesive failure	Average: 5.4 Maximum: 7.4 Minimum: 4.2 70 – 80 % cohesive failure 20 – 30 % adhesive failure	Passed
Adhesion values (MPa) – condensation chamber panels ³⁾	>3.5 adhesive failure >3.0 cohesive failure	Average: 5.6 Maximum: 6.9 Minimum: 4.1 70 – 80 % cohesive failure 20 – 30 % adhesive failure	Passed
Undercutting from scribe (mm) - average maximum values wave tank panels ⁴⁾	< 8	3.5	Passed
Cathodic disbondment (mm) – Wave tank bottom panel ⁵⁾	< 8	7.2	Passed
Current demand (mA/m ²) – bottom panel ⁵⁾	< 5	3.3	Passed
U-beam ¹⁾	No degradation (defects, cracking or detachment at the angle or weld)	No degradation	Passed

1) Details of blister and rust and u-beam in Table B-4 Appendix B.

2) Details of Pull-off adhesion test, wave tank and heat exposed panels in Table B-5 Appendix B.

3) Details of Pull-off adhesion test, condensation chamber in Table B-6 Appendix B.

4) Details of physical testing in Table B-7 Appendix B.

5) Details of Cathodic Protection in Table B-8 Appendix B.



7 CONCLUSION

The results from the testing show that Example Epoxy Paint from Example Coating Producer has passed all the requirements given in the Performance Standard for Protective Coatings /1/.

8 REFERENCES

/1/ MSC 215 (82) :2006 Performance Standard for Protective Coatings for dedicated sea water ballast tanks in all types of ships and double-side skin spaces of bulk carriers

9 APPENDIX A - ENVIRONMENTAL DATA - WEATHERING OF SHOP PRIMED PANELS

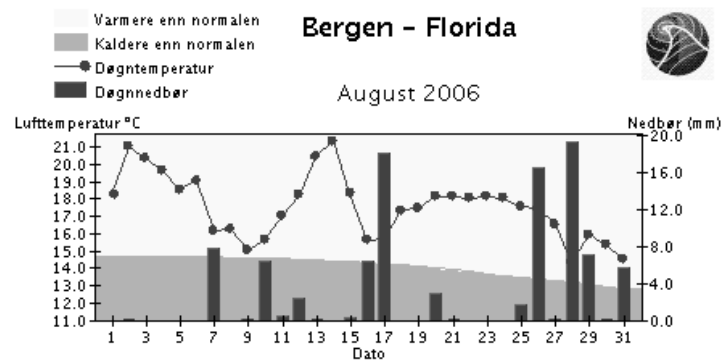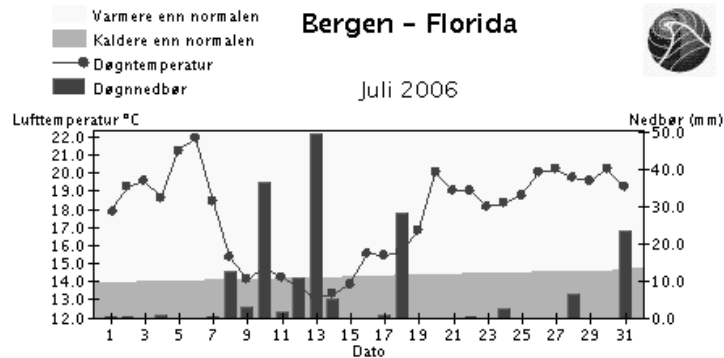

10 APPENDIX B - DETAILS OF SURFACE PREPARATION, APPLICATION AND TEST RESULTS

Table B-1 Surface preparation data.

Surface preparation date	November 2007 The prepared panels were stored at ambient in- door conditions until use
Surface preparation method	Blast cleaning
Blasting standard	Sa 2 ½
Abrasive used	AlSil A3+ steel shot
Roughness (µm)	R _{max} 50 -75
Water soluble salts	32, 38 and 40 mg / m ² Spot check performed on 3 out of 30 panels produced at the same time
Dust and abrasive inclusions	No dust or abrasive inclusions observed by visual examination.
Treatment of shopprimer after weathering	Low pressure washing
Water soluble salts after treatment of shopprimer	Spot check 28, 41 and 38 mg / m ²

Form 9-1 (Continued)

Table B-2 Application data.

Coating data:	Shop primer	1 st coat	2 nd coat
Paint system:	Example red	Example Epoxy Paint Al Grey	Example Epoxy Paint Buff
Manufacturer:	Example Coating Producer		
Date	20.11.07	22.01.08	23.01.08
Time	10:00	10:00	10:00
Batch No. curing agent			
Batch No. base			
Thinner name (if used)			
Batch No. thinner(if used)			
Equipment used	Graco King 68:1	Graco King 68:1	Graco King 68:1
Air pressure (bar)	100	170	170
Size nozzle (inches)	0.021	0.021	0.021
Fan width (°)	60	60	60
Mix. ratio (volume)	A: B = 3:1	3:1	3:1
Volume solid (volume)	30 ± 2	80	80
Wet film thickness (μ)	55-70	275	275
Dry film thickness (μ)	15-25	See Table 3	See Table 4
Thinner (%)	0	0	0
Air temperature (°C)	25	25	25
Humidity (% RH)	78	80	82
Steel temp. (°C)	25	25	25
Dew point (°C)	20	20	20
Present at application of shop primer: nn – MM Group (painter) and mm – laboratory. Present at application of test coating: kk - Example Coating Producer, nn – MM Group, and mm – laboratory.			
Comments:			

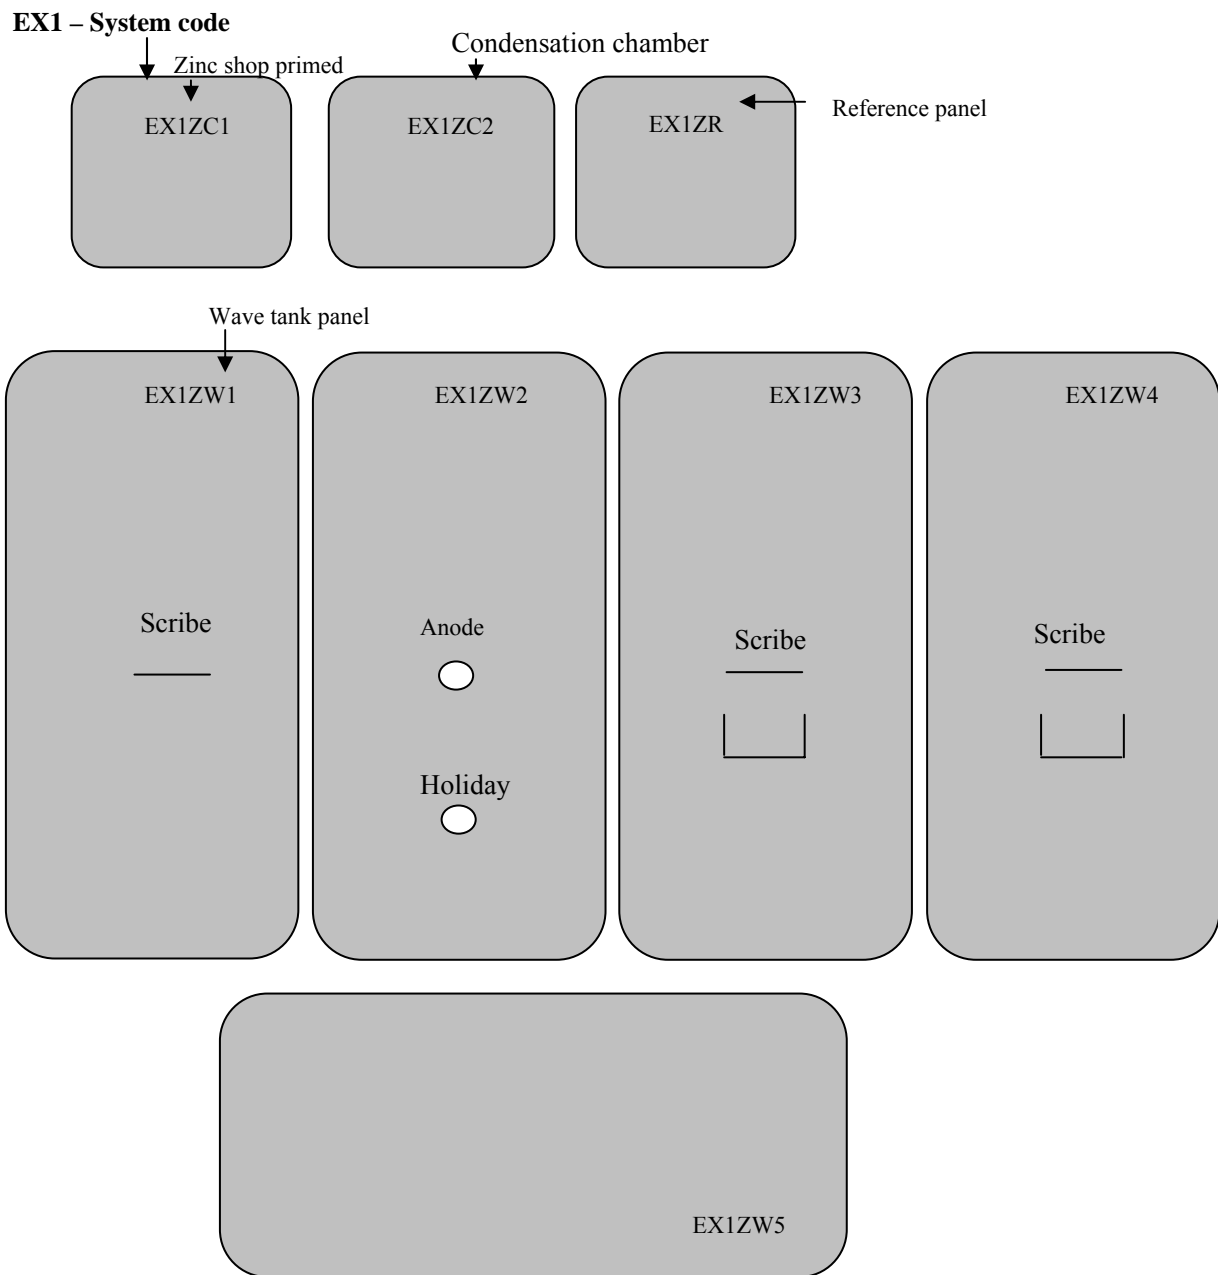


Figure B-1 Coding.

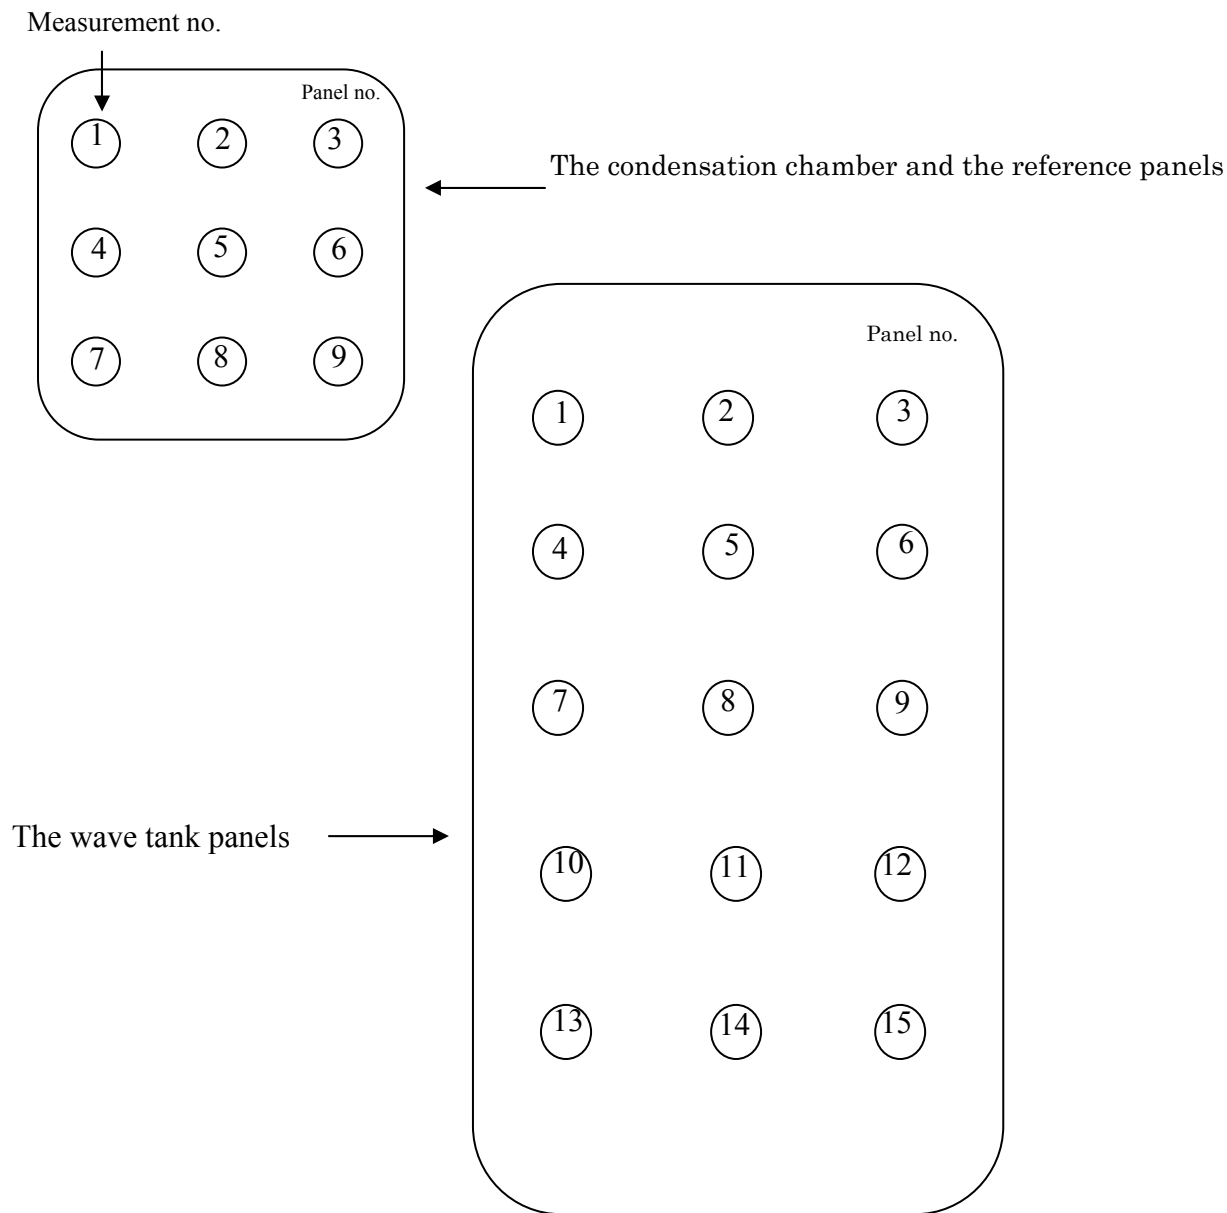


Figure B-2 Thickness measurement locations.

**Table B-3 Total Dry Film Thickness – Example Epoxy Paint
(20 µm subtracted for shop primed substrate).**

Measure ment	Panel no EX1-								
	ZW1	ZW2	ZW3	ZW4	ZW5	ZC1	ZC2	ZR	Total
1	332	330	338	322	324	325	320	354	
2	324	356	362	360	388	360	322	320	
3	320	320	328	326	336	342	334	322	
4	320	344	368	320	320	330	340	364	
5	352	356	412	350	326	346	358	336	
6	340	320	340	320	320	362	342	342	
7	320	326	366	356	320	340	330	320	
8	380	348	428	398	348	358	320	346	
9	338	320	380	364	330	338	322	320	
10	320	319	356	338	316				
11	342	360	408	456	340				
12	316	320	326	324	324				
13	320	344	356	332	320				
14	366	424	410	380	366				
15	342	348	330	350	346				
Max	380	424	428	456	388	362	358	364	456
Min	316	319	326	320	316	325	320	320	316
Average	335	342	367	353	335	345	332	336	344
StDev	19	27	34	37	20	13	13	17	27

Table B-4 Development of blisters and rust after exposure.

Code	Description	Blister size	Blister density	Rust	Other defects
EX1ZW1	Top wave tank panel with scribe	0	0	0	0
EX1ZW2	Bottom wave tank panel with anode	0	0	0	0
EX1ZW3	Side wave tank panel with scribe and U-beam Cooling	0	0	0	0
EX1ZW4	Side wave tank panel with scribe and U-beam No cooling	0	0	0	0
EX1ZW5	Panel exposed to 70 °C air (heating chamber)	0	0	0	0
EX1ZC1	Condensation chamber	0	0	0	0
EX1ZC2	Condensation chamber	0	0	0	0

Table B-5 Results of the Pull-off adhesion test, wave tank and heat exposed panels.

Panel no.	Adhesion strength (MPa)	Fracture
Top wave tank panel with scribe W1	4.5	30 % B, 20 % C, 30 % C/D, 20 % D
	5.2	20 % B, 30 % C, 30 % C/D, 20 % D
	4.8	30 % B, 20 % C, 20 % C/D, 30 % D
Bottom wave tank panel with anode W2	5.3	30 % B, 20 % C, 20 % C/D, 30 % D
	4.2	30 % B, 20 % C, 30 % C/D, 20 % D
	6.1	20 % B, 30 % C, 30 % C/D, 20 % D
Side wave tank panel with scribe and U-beam Cooling W3	7.0	20 % B, 30 % C, 30 % C/D, 20 % D
	4.6	30 % B, 20 % C, 20 % C/D, 30 % D
	5.3	30 % B, 20 % C, 30 % C/D, 20 % D
Side wave tank panel with scribe and U-beam No cooling W4	5.3	30 % B, 20 % C, 30 % C/D, 20 % D
	7.4	20 % B, 30 % C, 30 % C/D, 20 % D
	5.1	30 % B, 20 % C, 20 % C/D, 30 % D
Panel exposed to 70 °C air (heating chamber) W5	4.6	30 % B, 20 % C, 20 % C/D, 30 % D
	6.6	30 % B, 20 % C, 30 % C/D, 20 % D
	5.3	20 % B, 30 % C, 30 % C/D, 20 % D
Average	5.4	70 – 80 % Cohesive failure, 20 – 30 % Adhesive
Max	7.4	
Min	4.2	

A/B Fracture between the steel surface and 1st coat (shop primer).
 B Fracture in the 1st coat.
 B/C Fracture between the 1st and 2nd coat.
 C Fracture in the 2nd coat.
 C/D Fracture between the 2nd and 3rd coat.
 D Fracture in the 3rd coat
 -/Y Fracture between the outer coat and the glue.

Table B-6 Results of the Pull-off adhesion test, condensation chamber and reference panels.

Condensation chamber panel C1	6.1	20 % B, 30 % C, 30 % C/D, 20 % D
	4.1	30 % B, 20 % C, 20 % C/D, 30 % D
	6.9	30 % B, 20 % C, 30 % C/D, 20 % D
Condensation chamber panel C2	4.6	30 % B, 20 % C, 30 % C/D, 20 % D
	5.2	20 % B, 30 % C, 30 % C/D, 20 % D
	6.4	30 % B, 20 % C, 20 % C/D, 30 % D
Average	5.6	70 – 80 % Cohesive failure, 20 – 30 % Adhesive
Max	6.9	
Min	4.1	
Reference panel (not exposed) R	4.1	30 % B, 20 % C, 20 % C/D, 30 % D
	4.5	30 % B, 20 % C, 30 % C/D, 20 % D
	5.0	20 % B, 30 % C, 30 % C/D, 20 % D

A/B Fracture between the steel surface and 1st coat (shop primer).
 B Fracture in the 1st coat.
 B/C Fracture between the 1st and 2nd coat.
 C Fracture in the 2nd coat.
 C/D Fracture between the 2nd and 3rd coat.
 D Fracture in the 3rd coat
 -/Y Fracture between the outer coat and the glue.

Table B-7 Results of physical testing.

Panel	Undercutting from scribe (mm)*	Flexibility**	Comment
Top wave tank panel EX1ZW1	5.7	150 mm	≤ 2 % elongation
Cooled side wave tank panel EX1ZW3	2.2	NA	
Not cooled side wave tank panel EX1ZW4	2.6	NA	
Average	3.5		
Reference panel (not exposed) EX1ZR	Not applicable	75 mm	≤ 4 % elongation

* Evaluated by scraping with knife.

** Flexibility¹⁾ modified according to panel thickness (3 mm steel, 300 µm coating, 150 mm cylindrical mandrel gives 2% elongation) for information only; 1) Reference standards: ASTM D4145:1983. Standard Test Method for Coating Flexibility of Prepainted Sheet.

Undercutting from scribe:

“Rinse the test panel with fresh tap water immediately after exposure, blowing off residues of water from the surface using compressed air if necessary, and inspect for visible changes. Carefully remove any loose coating using a knife blade held at an angle, positioning the blade at the coating/substrate interface and lifting the coating away from the substrate.” (From ISO 4328-8:2005, section 5.3.1.)

“Calculate the degree of delamination d , in millimetre using the equation $d=(d1-w)/2$ where $d1$ is the mean overall width of the zone of delamination, in millimetres; w is the width of the original scribe, in millimetres.” (From ISO 4328-8:2005, section 6.1.)

“Calculate the degree of corrosion c , in millimetre using the equation $c=(wc-w)/2$ where wc is the mean overall width of the zone of corrosion, in millimetres; w is the width of the original scribe, in millimetres.” (From ISO 4328-8:2005, section 6.2.)

Additionally IACS interpretation of IMO PSPC: Undercutting from scribe can be either corrosion of the steel substrate or delamination between the shop primer and the epoxy coating (compatibility test). For PSPC maximum width is used (MSC.215(82), Appendix 1, section 2.2.6 and not mean overall width as in the ISO standard. The average of the three maximum records (three panels with scribe) is used for acceptance and shall be less than 8 mm for epoxy based systems to be acceptable. Cohesive adhesion failure in the shop primer is not to be included as part of the delamination.

Table B-8 Results of Cathodic Protection (CP).

Panel	Cathodic disbondment (mm)	Blisters / rust	Zinc anode weight loss (g)	Current demand (mA/ m ²)
EX1ZW2	7.2	0	1.2345	3.32

Exposure time: 120 days (Total time 180 days. Each cycle consists of 2 weeks seawater immersion and 1 week exposure in air)

Utilisation factor: 0.8

Consumption rate for Zn-anodes: 11.3 kg/A year

Cathodic protection; disbonding from artificial holiday:

“On completion of the test, thoroughly rinse the panel with tap water, taking care not to damage the coating.” (From ISO 15711:2003)

“Assess loss of adhesion at the artificial holiday by using a sharp knife to make two cuts through the coating to the substrates, intersection at the holiday. With the point of the knife, attempt to lift and peel back the coating from around the holiday. Record whether the adhesion of the coating to the substrate has been reduced and the approximate distance, in millimetres, that the coating can be peeled.” (From ISO 15711:2003)

Additionally IACS interpretation of IMO PSPC: Repeat the cutting and lifting all around the artificial holiday to find the maximum loss of adhesion. Disbonding from artificial holiday can be either loss of adhesion to the steel substrate or between the shop primer and the epoxy coating and shall be less than 8 mm for epoxy based systems to be acceptable (compability test). Cohesive adhesion failure in the shop primer is not to be included as part of the loss of adhesion.

11 APPENDIX C – PHOTO DOCUMENTATION

(It should be overview pictures of the panels and close up pictures of the undercutting from scribe and the disbonding from artificial holiday)

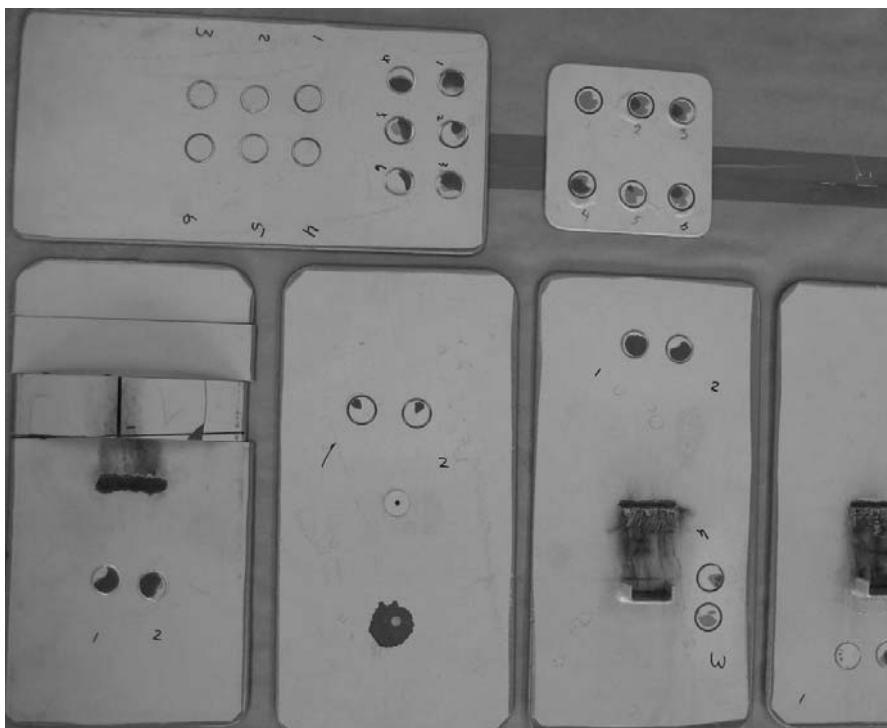


Figure C-1 Overview picture of the panels after exposure in the wave tank and the heating chamber. Reference panel not exposed on the top right. Picture taken after examination (example picture not connected to example results in this model report).

Picture missing

Figure C-2 Overview picture of the panels exposed in condensation chamber (example picture not connected to example results in this model report).

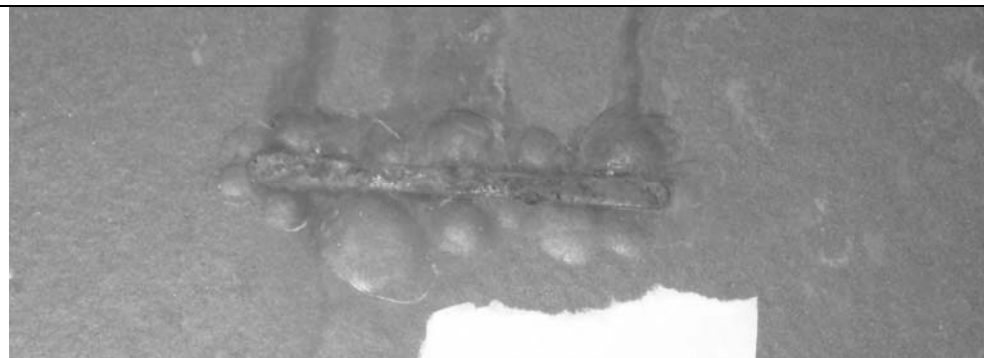


Figure C-3 Scribe area of top wave tank panel before removing of loose coating (example picture not connected to example results in this model report).

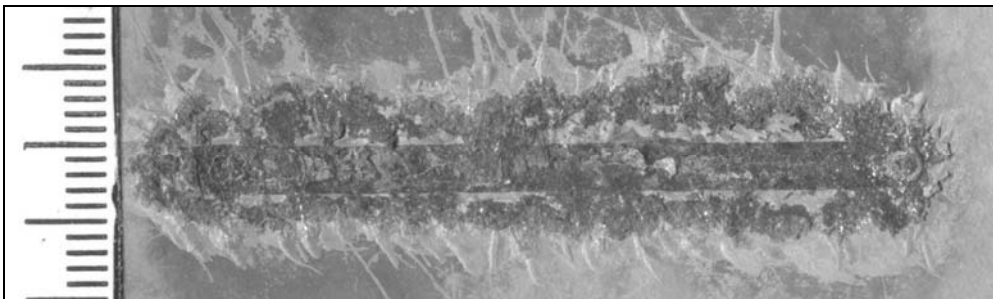


Figure C-4 Undercutting from scribe, top wave tank panel (example picture not connected to example results in this model report).

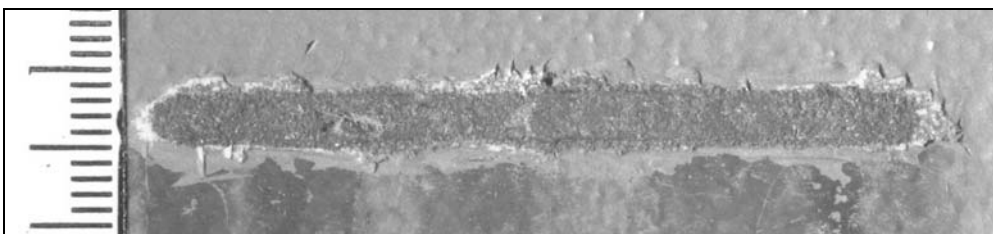


Figure C-5 Undercutting from scribe, side wave tank panel without cooling (example picture not connected to example results in this model report).

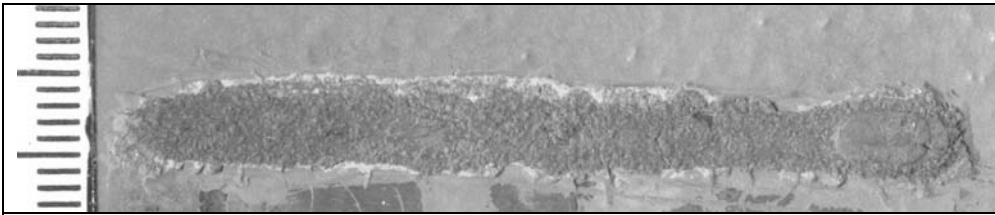


Figure C-6 Undercutting from scribe, side wave tank panel with cooling (example picture not connected to example results in this model report).

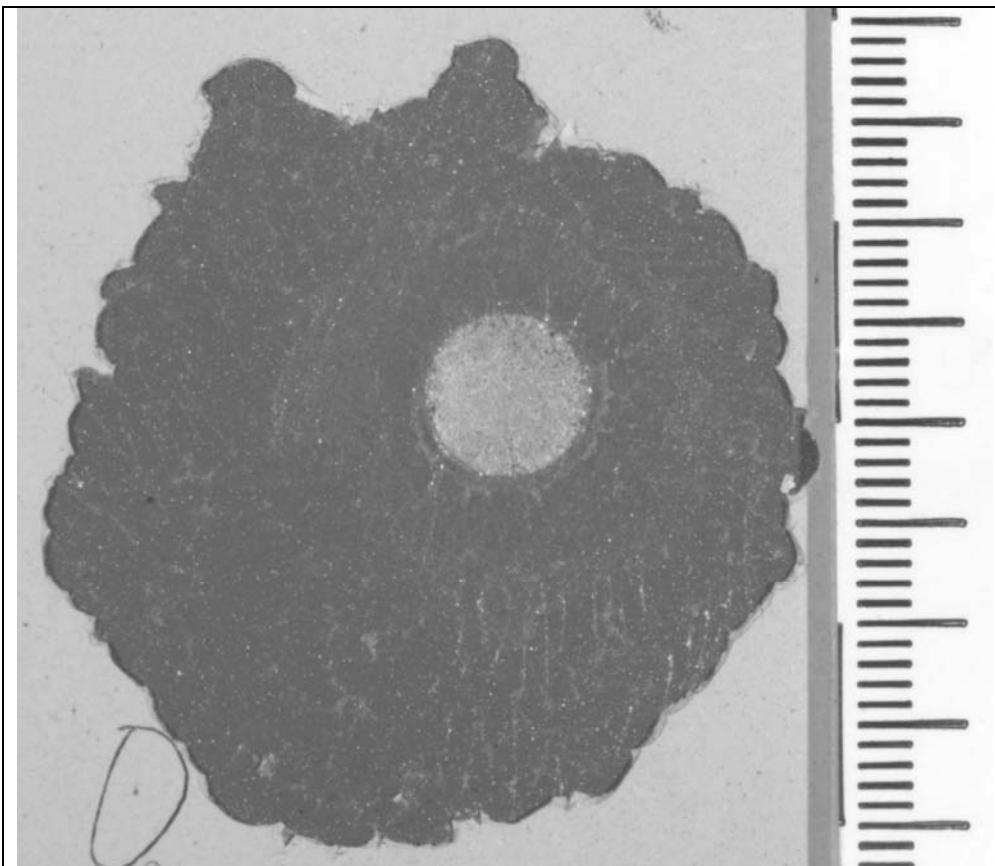


Figure C-7 Disbonding from artificial holiday, bottom wave tank panel (example picture not connected to example results in this model report).

12 APPENDIX D - INFRARED SCANNING CHARTS

Figure D-1

Figure D-2

Figure D-3

Figure D-4

Figure D-5

Figure D-6

EXAMPLE COATING PRODUCER

BALLAST TANK COATING TEST OF 2 * 160 μ M EXAMPLE EPOXY PAINT ON EXAMPLE SHOP PRIMER

Table of contents

1	Summary
2	Scope of work
3	Work carried out prior to exposure
3.1	Identification
3.2	Surface preparation
3.3	Application
3.3.1	Application procedure
3.3.2	Coding
3.4	Dry film thickness
3.5	Pin hole detection
4	Exposure
5	Tests carried out after exposure
6	Test results
7	Conclusion
8	References
9	Appendix A - Environmental data - weathering of shop primed panels
10	Appendix B - Details of surface preparation, application and test results
11	Appendix C - Photo documentation
12	Appendix D - Infrared Scanning Charts

1 SUMMARY

The coating system, 2 * 160 µm Example Epoxy Paint from Example Coating Producer, applied to Example zinc silicate shop primed panels has been tested in accordance with the IMO Performance Standard for protective Coatings /1/, section 1.7 of appendix 1 to annex 1 without wave movement (crossover test). The coating was applied after 2 months weathering of the shop primer.

The results from the testing show that the Example Epoxy Paint from Example Coating Producer has passed all the requirements given in the Performance Standard for Protective Coatings /1/.

2 SCOPE OF WORK

The following work and tests have been performed:

- Identification of the coating system
- Film thickness measurements and pin hole detection on panels before testing
- 180 days testing in wave tank conditions, but without wave movement
- Evaluation of results after testing, including blister detection, disbonding from artificial holiday and adhesion

3 WORK CARRIED OUT PRIOR TO EXPOSURE

3.1 Identification

The coating system was identified by infrared scanning (by means of a(name and model of the instrument)), and by determination of specific gravity (according to ISO 2811 -1) by means of an Pyknometer (name and model of the instrument).

3.2 Surface preparation

Surface preparation was carried out according to the data given in Table B-1 Appendix B.

3.3 Application

3.3.1 Application procedure

Example zinc silicate shop primer was applied to the blast cleaned panels according to the data given in Table 2. The shop primed panel were then exposed out-door for 2 months. The environmental data for the exposure period is given in Appendix A.

Two coats (specified dry film thickness 160 µm per coat) of Example Epoxy Paint were applied to the weathered and cleaned zinc silicate shop primed panel. The application data are given in Table B-2 Appendix B.

3.3.2 Coding

The panel were coded as shown in Figure B-1 in Appendix B.

3.4 Dry film thickness

The dry film thickness measurements were carried out by means of a (name and model of the instrument) dry film thickness unit before testing. Templates, as given in Figure B-2 in Appendix B, were used for the measurements. The results from the measurements are given in Table B-3 in Appendix B.

3.5 Pin hole detection

Pin hole detection was performed on the coated test panel before testing. The detection was carried out by means of a (name and model of the instrument) Pinhole detector at 90 volts.

4 EXPOSURE

The testing was carried out according to the IMO Performance Standard for Protective Coatings /1/. The exposure was started 02.11.07 and terminated 14.06.08.

5 TESTS CARRIED OUT AFTER EXPOSURE

Evaluation of blisters and rust, adhesion, undercutting from scribe and flexibility was carried out according to specifications and standards referred to in the IMO Performance Standard /1/.

6 TEST RESULTS

The results of the product identification are given in Table 1.

The results of the examination of the coated test panels are schematically given in Table 2 and more detailed in Appendix B. Pictures of the panels after exposure are enclosed as Appendix C.

Table 1 Results of analyses (Product identification)

Product	Batch no.	IR identification (main components)	Specific gravity (g/cm ³)
Example, part A	123	Ethyl silicate	0.93
Example, part B	234	NA*	2.21
Example Epoxy Paint Grey, base	345	Epoxy	1.48
Example Epoxy Paint hardener	456	Amide	0.96
Example Epoxy Paint Buff, base	567	Epoxy	1.47

*Identified and spectres stored. No generic correlation to the spectres in the data base found.

Table 2 Results of examination of the coated test samples

Test parameter	Acceptance criteria	Test results	Passed / failed
Pin holes (no)	No pinholes	0	Passed
Blisters and rust ¹⁾	No blisters or rust	0	Passed
Adhesion values (MPa) ²⁾	>3.5 adhesive failure >3.0 cohesive failure	Average: 5.2 Maximum: 6.1 Minimum: 4.2 70 – 80 % cohesive failure 20 – 30 % adhesive failure	Passed
Cathodic disbondment (mm) ³⁾	< 8	7.2	Passed
Current demand (mA/m ²) ³⁾	< 5	3.3	Passed

1) Details of blister and rust Table B-4 Appendix B.

2) Details of Pull-off adhesion test in Table B-5 Appendix B.

3) Details of Cathodic Protection in Table B-6 Appendix B.



7 CONCLUSION

The results from the testing show that Example Epoxy Paint from Example Coating Producer has passed all the requirements for the crossover test given in the Performance Standard for Protective Coatings /1/.

8 REFERENCES

/1/ MSC 215 (82) :2006 Performance Standard for Protective Coatings for dedicated sea water ballast tanks in all types of ships and double-side skin spaces of bulk carriers

9 APPENDIX A - ENVIRONMENTAL DATA - WEATHERING OF SHOP PRIMED PANELS

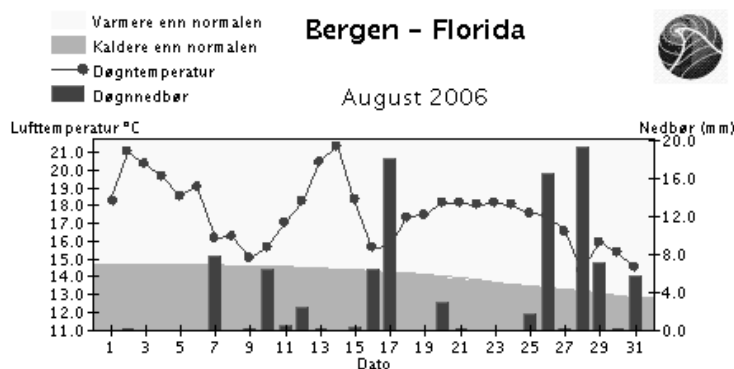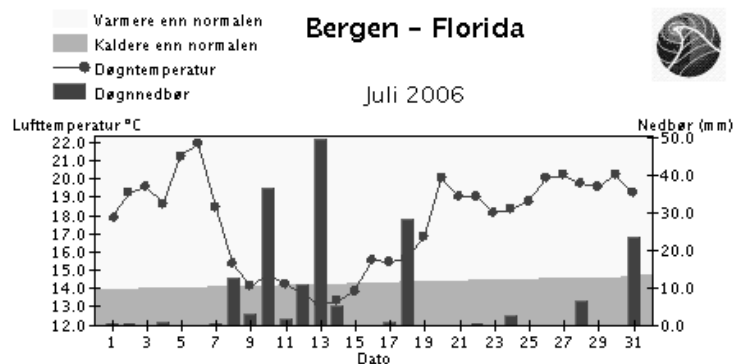

10 APPENDIX B - DETAILS OF SURFACE PREPARATION, APPLICATION AND TEST RESULTS

Table B-1 Surface preparation data.

Surface preparation date	November 2007 The prepared panels were stored at ambient in- door conditions until use
Surface preparation method	Blast cleaning
Blasting standard	Sa 2 ½
Abrasive used	AlSil A3+ steel shot
Roughness (µm)	R _{max} 50 -75
Water soluble salts	32, 38 and 40 mg / m ² Spot check performed on 3 out of 30 panels produced at the same time
Dust and abrasive inclusions	No dust or abrasive inclusions observed by visual examination.
Treatment of shopprimer after weathering	Low pressure washing
Water soluble salts after treatment of shopprimer	Spot check 28, 41 and 38 mg / m ²

Form 9-2 (Continued)

Table B-2 Application data.

Coating data:	Shop primer	1 st coat	2 nd coat
Paint system:	Example red	Example Epoxy Paint Al Grey	Example Epoxy Paint Buff
Manufacturer:	Example Coating Producer		
Date	20.11.07	22.01.08	23.01.08
Time	10:00	10:00	10:00
Batch No. curing agent			
Batch No. base			
Thinner name (if used)			
Batch No. thinner(if used)			
Equipment used	Graco King 68:1	Graco King 68:1	Graco King 68:1
Air pressure (bar)	100	170	170
Size nozzle (inches)	0.021	0.021	0.021
Fan width (°)	60	60	60
Mix. ratio (volume)	A: B = 3:1	3:1	3:1
Volume solid (volume)	30 ± 2	80	80
Wet film thickness (μ)	55-70	275	275
Dry film thickness (μ)	15-25	See Table 3	See Table 4
Thinner (%)	0	0	0
Air temperature (°C)	25	25	25
Humidity (% RH)	78	80	82
Steel temp. (°C)	25	25	25
Dew point (°C)	20	20	20

Present at application of shop primer: nn – MM Group (painter) and mm – laboratory. Present at application of test coating: kk - Example Coating Producer, nn – MM Group, and mm – laboratory.

Comments:

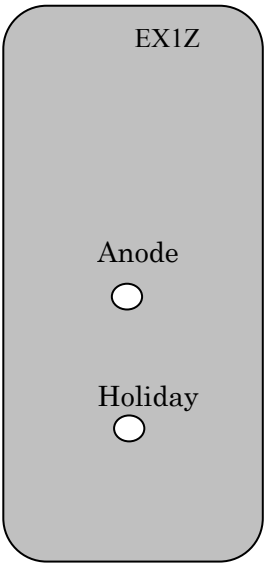


Figure B-1 Coding.

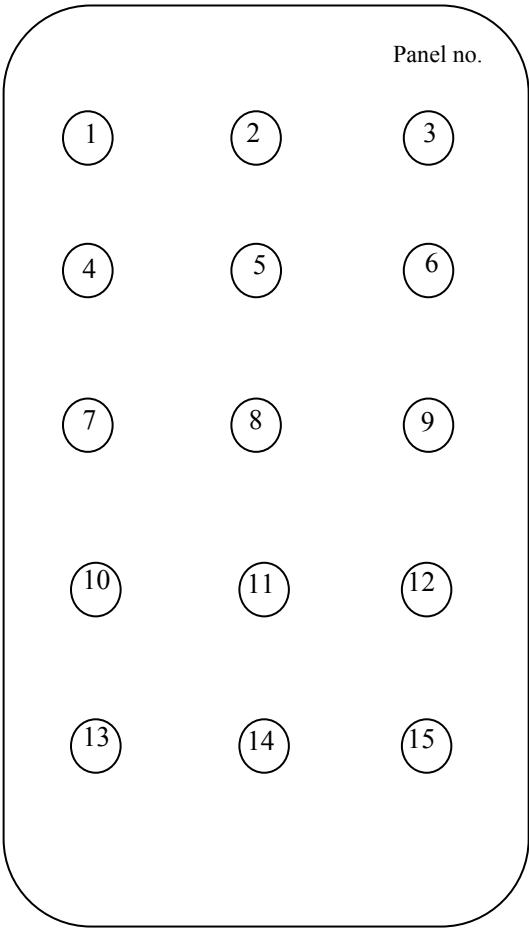


Figure B-2 Thickness measurement locations.

**Table B-3 Total Dry Film Thickness – Example Epoxy Paint
(20 µm subtracted for shop primed substrate).**

Measure ment	Panel no EX1ZW2
1	330
2	356
3	320
4	344
5	356
6	320
7	326
8	348
9	320
10	319
11	360
12	320
13	344
14	424
15	348
Max	424
Min	319
Average	342
StDev	27

Table B-4 Development of blisters and rust after exposure.

Code	Description	Blister size	Blister density	Rust	Other defects
EX1ZW2	Bottom wave tank panel with anode	0	0	0	0

Table B-5 Results of the Pull-off adhesion test, wave tank and heat exposed panels.

Panel no.	Adhesion strength (MPa)	Fracture
Bottom wave tank panel with anode W2	5.3	30 % B, 20 % C, 20 % C/D, 30 % D
	4.2	30 % B, 20 % C, 30 % C/D, 20 % D
	6.1	20 % B, 30 % C, 30 % C/D, 20 % D
Average	5.2	70 – 80 % Cohesive failure, 20 – 30 % Adhesive
Max	6.1	
Min	4.2	

A/B Fracture between the steel surface and 1st coat (shop primer).
 B Fracture in the 1st coat.
 B/C Fracture between the 1st and 2nd coat.
 C Fracture in the 2nd coat.
 C/D Fracture between the 2nd and 3rd coat.
 D Fracture in the 3rd coat
 -/Y Fracture between the outer coat and the glue.

Table B-8 Results of Cathodic Protection (CP).

Panel	Cathodic disbondment (mm)	Blisters / rust	Zinc anode weight loss (g)	Current demand (mA/ m ²)
EX1ZW2	7.2	0	1.2345	3.32

Exposure time: 120 days (Total time 180 days. Each cycle consists of 2 weeks seawater immersion and 1 week exposure in air)

Utilisation factor: 0.8

Consumption rate for Zn-anodes: 11.3 kg/A year

Cathodic protection; disbonding from artificial holiday:

“On completion of the test, thoroughly rinse the panel with tap water, taking care not to damage the coating.” (From ISO 15711:2003)

“Assess loss of adhesion at the artificial holiday by using a sharp knife to make two cuts through the coating to the substrates, intersection at the holiday. With the point of the knife, attempt to lift and peel back the coating from around the holiday. Record whether the adhesion of the coating to the substrate has been reduced and the approximate distance, in millimetres, that the coating can be peeled.” (From ISO 15711:2003)

Additionally IACS interpretation of IMO PSPC: Repeat the cutting and lifting all around the artificial holiday to find the maximum loss of adhesion. Disbonding from artificial holiday can be either loss of adhesion to the steel substrate or between the shop primer and the epoxy coating and shall be less than 8 mm for epoxy based systems to be acceptable (compatibility test). Cohesive adhesion failure in the shop primer is not to be included as part of the loss of adhesion.

11 APPENDIX C – PHOTO DOCUMENTATION

(It should be overview picture of the panel and close up picture of the disbonding from artificial holiday)

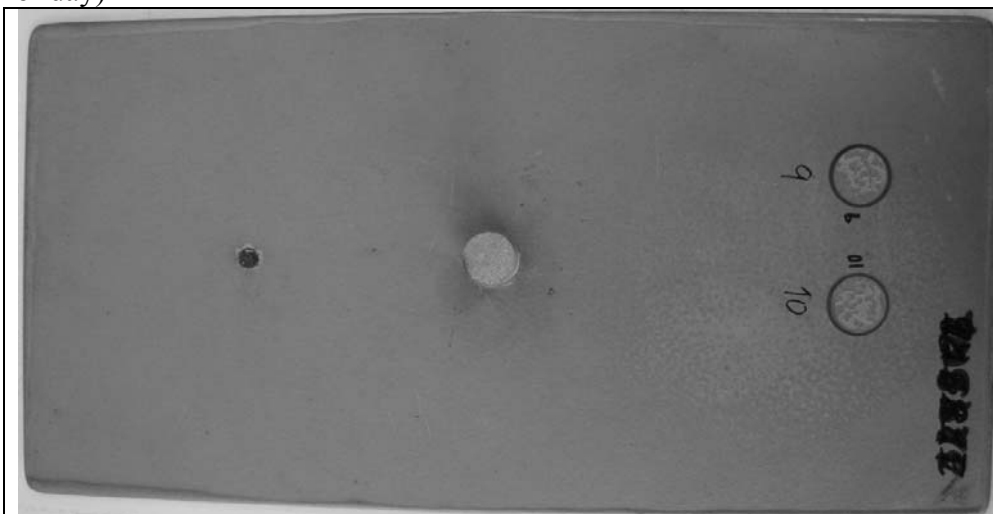


Figure C-1 Disbonding from artificial holiday, bottom wave tank panel (example picture not connected to example results in this model report).



Figure C-2 Disbonding from artificial holiday, bottom wave tank panel (example picture not connected to example results in this model report).

12 APPENDIX D - INFRARED SCANNING CHARTS

Figure D-1

Figure D-2

Figure D-3

Figure D-4

Figure D-5

Figure D-6

EFFECTIVE DATE AND APPLICATION (Amendment 1-2)

1. The effective date of the amendments is 15 April 2009.
2. This amendments of the Rules may not apply to the service suppliers approved by the Society before the effective date until the valid date their approval.